

Name: 1" PolySorb Foundation Colors Collection
 Size Available: 4' x 8', 4' x 10' standard. Custom colors and sizes up to 5' x 12' available. Longer lead times and MOQ may apply.
 Thickness: 1 inch
 Core Density: 7.0 - 7.5lbs
 NRC: 0.70 - 0.85 (BFCC)
 Face Type: Ironed Smooth Face
 FSI: Class A Flame Spread Index

1" THICK FOUNDATION COLORS



Core Color: White, Cloud, Light Beige, Dark Beige, Light Grey, Grey, Medium Grey, Charcoal, Obsidian, Charcoal Core Black Face, Tan, Chestnut Brown

Intertek Report #200421005SHF-001 Description of the test specimen

Name: PS1
 Specimen Size: 10.80m2
 Mount Method: Type A Mounting Method
 Frame Construction: **Placed Directly on The Floor**

Area of test specimen: 72. ft2
 Air temp in the test room: 23°C
 Air humidity in test room: 53%

Number of sound source positions: 2
 Number of microphone positions per sound source position: 8
 Type of noise used: Pink Random Noise
 Type of mounting used: Type A Mounting

Frequency f Hz	T1 - Empty Chamber	Tc - With Sample	One-Third Octave
100	0.00	0.04	2.87
125	0.00	0.07	5.16
160	0.00	0.12	8.53
200	0.00	0.20	14.17
250	0.00	0.28	20.06
315	0.00	0.35	25.23
400	0.00	0.50	36.15
500	0.00	0.63	45.52
630	0.00	0.75	53.71
800	0.00	0.83	59.97
1000	0.00	0.87	62.51
1250	0.00	0.94	67.90
1600	0.00	0.95	68.12
2000	0.00	0.99	71.59
2500	0.00	1.01	72.80
3150	0.00	1.01	72.48
4000	0.00	0.98	70.60
5000	0.00	0.97	70.12


Hz	Xp
125	0.15
250	0.15
500	0.45
1000	0.75
2000	0.95
4000	0.95

Practical sound absorption coefficients

Evaluation based on laboratory measurement results obtained by an engineering method.

Ratings according to ISO 11654
 Weighted sound absorption coefficient: 0.80
 Sound absorption class: A

Rating according to ASTM C423 - 99
 Noise Reduction Coefficient = 0.85
 Sound Absorption Average = 0.82

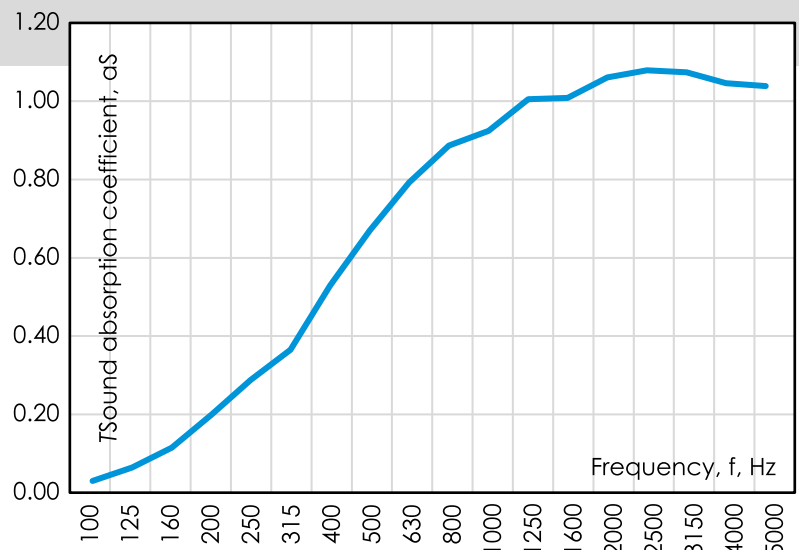

It is strongly recommended to use this single number rating in combination with the complete sound absorption coefficient curve.
 Sound absorption coefficients according to ISO 354 measurement of sound absorption in a reverberation room.

1" THICK FOUNDATION COLORS



Name: 1" PolySorb Foundation Colors Collection
Size Available: 4' x 8', 4' x 10' standard. Custom colors and sizes up to 5' x 12' available. Longer lead times and MOQ may apply.

Thickness: 1 inch
Core Density: 7.0 - 7.5lbs
NRC: 0.70 - 0.85 (BFCC)
Face Type: Ironed Smooth Face
FSI: Class A Flame Spread Index

Core Color: White, Cloud, Light Beige, Dark Beige, Light Grey, Grey, Medium Grey, Charcoal, Obsidian, Charcoal Core Black Face, Tan, Chestnut Brown

